

## Intercalation and Exfoliation Mechanism of Kaolinite During the Emulsion Polymerization

José C. M. Neto<sup>\*a</sup>, Solenise Pinto Rodrigues Kimura<sup>a</sup>, Melissa Gurgel Adeodato<sup>b</sup>, João Evangelista Neto<sup>a</sup>, Nayra Reis do Nascimento<sup>b</sup>, Liliane Maria Ferrareso Lona<sup>b</sup>

<sup>a</sup>Department of Materials Engineering, School of Engineering, Amazonas State University, Rua Darcy Vargas, 1200, Parque Dez de Novembro, CEP: 69065-020, Manaus, Amazon, Brazil.

<sup>b</sup>Department of Materials Engineering and Bioprocess, Faculty of Chemical Engineering, University of Campinas, Rua Albert Einstein, 500, Cidade Universitária Zeferino Vaz, Barão Geraldo, CEP: 13083-852, Campinas, São Paulo, Brazil. [jotacostaneto@gmail.com](mailto:jotacostaneto@gmail.com) or [jmacedo@uea.edu.br](mailto:jmacedo@uea.edu.br)

Layered clays have been used as reinforcement in polymer nanocomposites by having a structure of silicate layers, cation exchange capacity, organically modified and have high aspect ratios. The aspect ratio of these layers is defined by (ratio diameter/thickness) is particularly high, with values greater than 1000. In general, nanomaterials provide reinforcing efficiency because of their high aspect ratios. Kaolin is natural clay which is the characteristic clay mineral kaolinite that have chemical composition  $\text{Al}_2\text{O}_3 \cdot 2\text{SiO}_2 \cdot 2\text{H}_2\text{O}$  and as a 1:1 dioctahedral phyllo-silicate in nature. The distance between the silicate layers is 0.72 nm and the layer thickness is 0.437 nm. Nanocomposites that use kaolin presented excellent thermal properties, flame retardant, barrier and mechanical. Concerning the methods for polymer nanocomposites synthesis, the most employed are melt blending and in situ polymerization. In this paper, we studied the mechanism of kaolinite during the in situ emulsion polymerization to production of polystyrene nanocomposites filled with kaolinite. The polymer nanocomposites were characterized by X-ray diffraction (XRD), Transmission Electron Microscopy (TEM) and Scanning Electron Microscopy (SEM).

### 1. Introduction

Polymer nanocomposites is a class of material where the load is at least one of their dimensions in nanometric size (1-100nm) dispersed in a polymer matrix (Kim and Palomino, 2011). The morphology of nanoparticles used in nanocomposites is shaped like nano-spheres, nanofibers, nanotubes, nanowires and layered nanomaterial (Ma and Zhang, 2014; Chiu et al., 2014; Imai, 2010; Romero-Ibarra et al., 2012). Nano-fillers widely used in polymeric nanocomposites are natural layered clays (Villanueva et al., 2014). Among the natural layered clays, the kaolinite stands out to be abundant in nature and chemically inert. Clays present several advantages to the preparation of nanocomposites. They are the nano-filler most abundantly available, can be easily dispersed in the majority of polymers, present high chemical intercalation ability and can be organically modified. The resulting properties of the final material can be superior to the properties of other engineering materials, such as pure polymers, microcomposites and the traditional polymeric composites (Akinci et al., 2014). Compared to polymer composites, the nanocomposites that use clays as reinforcement can show better gas and membrane barrier properties (due to the high aspect ratio of the clays), flammability and thermal resistance (due to high energy binding of clay silicates and low thermal expansion in comparison to metals and polymers) and electrical properties (due to the ability to exchange cations or transfer protons from water in the interlayer) (Paul and Robeson, 2008).

In the production of polymer nanocomposites using clays as nano-reinforcement, the compatibility polymer-clay is fundamental to achieve desired properties for the nanocomposite and a stable latex. In this sense usually the clay needs to suffer a pre-treatment before being added. This pre-treatment consists in intercalate a substance such as dimethylsulfoxide (DMSO), 6-aminohexane acid (AHA), N-methylformamide and dodecylamine (NMF-DDMNA), carboxylic acid and functionalized ammonia and urea in the clay. The amount

and kind of organic modifier can have a direct effect in the stability of the latex (Wang et al., 2010; Itagaki et al., 2001; Ammala et al., 2007; Essaway et al., 2009; Yilmaz et al., 2012).

Besides compatibility, the dispersion of the clays in the matrix is important, because, in nanometric scale, leads to a better interaction between clay and polymer. The kinds of morphologies of the clays inside the polymer matrix are: tactoid (agglomerates), intercalated (aggregated) and exfoliated (dispersed). The amount of intercalated and exfoliated clay interacting with the polymer chains is responsible for the improvement in the mechanical, thermal and barrier properties, being the exfoliated morphology the preferred because it gives the best properties. Other factors affecting the stability of the latex are the amount of clay used and the presence of polymer stabilizing agents (Yilmaz et al., 2012).

In this paper showed the intercalation/exfoliation mechanism of kaolinite during *in situ* emulsion polymerization to production of polystyrene nanocomposites filled with kaolinite.

## 2. Experimental

### 2.1 Reagents

The kaolinite from the State of Amazon, Brazil and processed by Arnil Union Northeast mining company (located in the State of Rio Grande do Norte, Brazil). Dimethylsulfoxide (DMSO, Synth), monomer styrene (St, Sigma Aldrich) washed four times with a 10 w/v% sodium hydroxide (Fmaia), potassium persulfate (KPS, Sigma Aldrich), sodium lauryl sulfate (SLS, Fmaia), hydroquinone (Sigma Aldrich). Distilled and deionized water.

### 2.2 Synthesis of the nanocomposite polystyrene / kaolinite

The synthesis of polystyrene/kaolinite nanocomposites was as follows: the desired amount of modified kaolinite was added into 133.90 g of styrene, and it was dispersed by a magnetic stirrer at 20 rpm at room temperature for 2 hours, followed by sonication for 24 min, the clay dispersion plus 537.94 g of water, an aqueous solution with 3.48 g of SLS and another with 0.57 g of KPS were added into a 1l batch reactor equipped (Figure 1) with a heating jacket, mechanical stirrer, reflux condenser, and purging tube. The stirring speed and nitrogen flux in the reactor were 60 rpm and 5 l/min, respectively. The reaction time was 90 minutes. To obtain samples in powder form for further characterization, the volatile liquids were evaporated in beakers in a laminar flow cabinet, and dried in an oven at 100 °C for 4 hours.

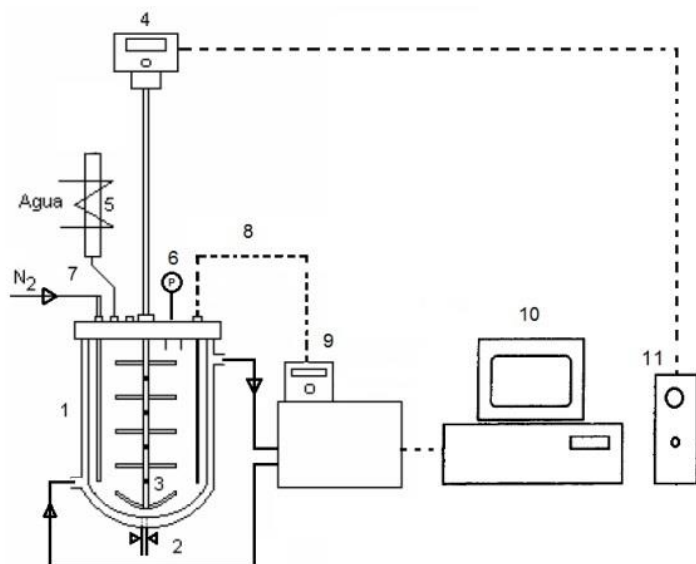


Figure 1. (1) Stainless steel reactor with heater jacket. (2) Sample collection valve bath (3/4) Stirrer, (5) Condenser, (6) Manometer, (7) Nitrogen line (g), (8) Thermocouple, (9) Thermostatic reactor bath, (10) Microcomputer with control and data capture system, (11) Agitation control.

### 2.3 X-ray Diffraction(XRD)

(Shimadzu, XRD 7000) with  $\text{CuK}\alpha$  radiation  $k = 1.54060 \text{ \AA}$  with  $2\theta$  varying between  $1.4\text{-}70^\circ$  was utilized for characterization of clay and nanocomposites.

## 2.4 High Resolution Transmission Electronic Microscope(HRTEM)

For the present work, a High Resolution Transmission Electronic Microscope JEOL, JEM 3010 URP, Japan, equipped with a camera CCD, Gatan MSC794, was used. The images were obtained with image capturing software Gatan, Digital Micrograph. The conditions for HRTEM were 300 kV tension, spot size = 1 $\mu$ m and  $\alpha$ -selector = 3, and beam current 111 $\mu$ A. Magnification was between 20,000-1,500,000. The powder nanocomposite samples were prepared and observed by HRTEM using an embedded method (Neto et al., 2015). In this method, the nanocomposite samples were macerated to obtain a thin and homogeneous powder, which was added and mixed into a solution of epoxy resin and catalyst. An ultramicrotome (Leica, Ultra Cutuct) was used to obtain thin sections (of around 120 nm in thickness) of cured epoxy resin containing the nanocomposite samples. The cut sections were placed on a carbon film coated copper grid of 3 mm of diameter.

## 2.5 Scanning Electronic Microscope (SEM)

Was used the TM-3000 model by Hitachi with DPI=95.91, Pixel Size=3310.55 AcceleratingVoltage=15,000 Volt. Preparation of sample for analysis in SEM: In the preparation of the latex sample, an aqueous solution of 5 ml of water and 5ml of alcohol and 5ml of the latex with 3% of clay was added. The mixture was added to a solution of Hand sprayer used to generate microdroplets. The microdrops were generated by the sprinkler to the sample holder. After addition of the microdroplets from the solution to the sample holder, the same was taken to a dissector for 24 hours prior to SEM analysis.

## 3 Results

The Figure 2a(i) shows XDR of kaolinite where it is observed the basal spacing ( $d_{001} = 0.72\text{nm}$ ,  $2\theta = 12.33^\circ$ ) (14). The Figure 2a(ii) and 2a(iii) shows XDR of polystyrene and nanocomposite polystyrene/kaolinite, respectively. The XRD of the formed nanocomposites (Figure 1a(iii)) illustrates the absence of any reflection pertaining to the presence of any remaining ordering of the kaolinite, this holds mainly for the layers that become exfoliated and/or intercalated within the polymer matrix (Essawy et al., 2009).

The clay, in intercalated form with ordered layers, as well as the polymer can be observed by Figure 2b. The monomer may have permeated between the layers of clay and polymerized, thus resulting in intercalation (Zhang et al., 2009).

Exfoliated clay morphologies are shown as dark lines in Figure 2b, randomly distributed, in the polymer matrix. These exfoliated structures show a total absence of order between clay layers. Even though kaolinite exfoliation is rare, due to the high cohesiveness between layers, it was possible to obtain a great amount of exfoliated clay in the polystyrene (Neto et al., 2015).

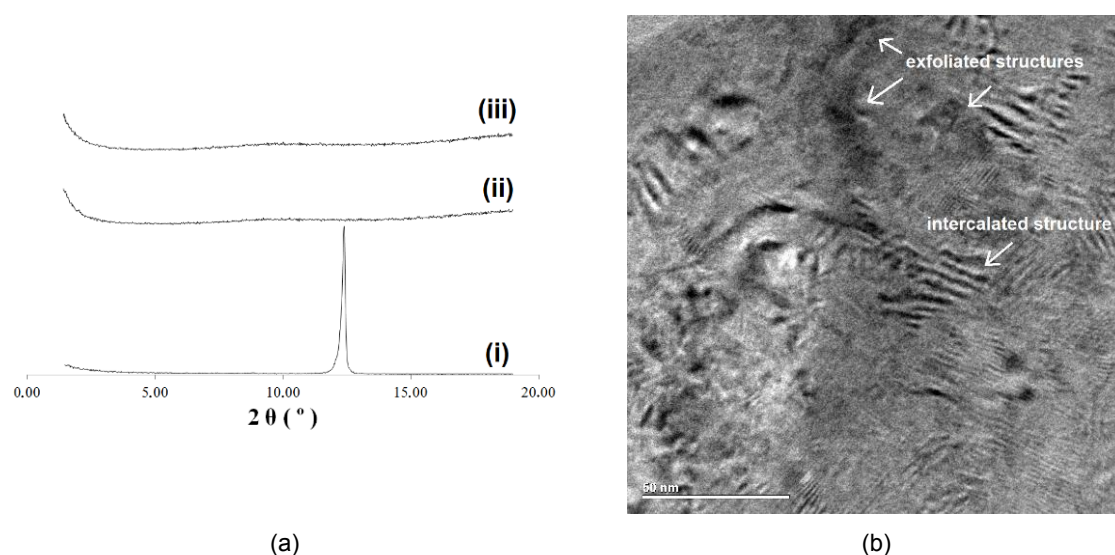


Figure 2. (a) XRD patterns of (i) Kaolinite, (ii) Polystyrene, (iii) Nanocomposite. (b) HRTEM image Clay disposition in the polymer matrix (PS). Magnification of 200k.



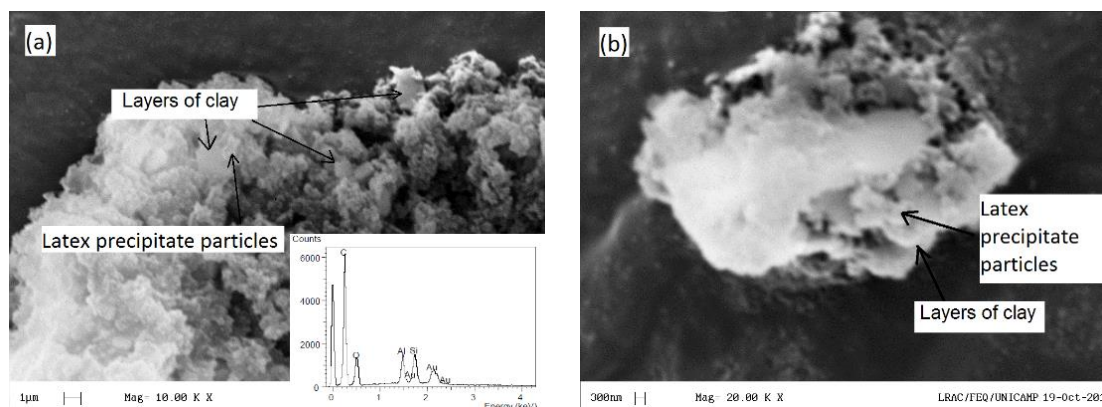


Figure 4. Latex precipitate 3% kaol-DMSO-PS. (a) Magnitude: 10k and (b) Magnitude: 20k.

#### 4. Conclusions

By means of the *in situ* polymerization technique it was possible to obtain polymer nanocomposite using kaolinite clay. The characterization by XRD and TEM showed that the layer morphology is intercalated and exfoliated. Through the study of several works it was possible to understand the mechanism of intercalation and exfoliation of the layers of the clay. The image by SEM proved the mechanism of intercalation and exfoliation of the clay layers.

#### Reference

- Ammala, A., Hill A. J.; Lawrence, K. A.; Tran T., 2007, Poly(m-xylene adipamide)-kaolinite and poly(m-xylene adipamide)-montmorillonite nanocomposites. *J. Appl. Polym. Sci.*, 104, 1377-1381.
- Akinci, A., Sen, S., Sen, U., 2014, Friction and wear behavior of zirconium oxide reinforced PMMA composites. *Composites: Part B* 56, 42-47.
- Chiu, C.-W., Huang, T.-K., Wang, Y.-C., Alamani, B.G., Lin, J.-J., 2014, Intercalation strategies in clay/polymer hybrids. *Prog. Polym. Sci.* 39, 443-485.
- Essawy, H. A., Youssef, A. M., Abd El-Hakim, A. A., Rabie, A. M., 2009, Exfoliation of Kaolinite Nanolayers in Poly(methylmethacrylate) Using Redox Initiator System Involving Intercalating Component. *Polym-Plast Technol.* 48, 177-184.
- Gardolinski, J. E., Carrera, L. C. M., Cantão, M. P., Wypych, F. J., 2000, Layered polymer-kaolinite nanocomposites, *Mater. Sci. Eng.* 35, 3113-3119.
- Hasegawa N. et al., 1999, Preparation and mechanical properties of polystyrene-clay hybrids. *J. Appl. Polym. Sci.*, v. 74, p. 3359-3364.
- Ham H. T., Choi Y. S., Chee M. G., Chung., 2006, In Jae. Singlewall carbon nanotubes covered with polystyrene nanoparticles by in-situ miniemulsion polymerization. *J. Polym. Sci., Part A: Polym. Chem* 44, 573-584.
- Ianchis, R.; Donescu, D.; Petcu, C.; Ghiurea, M.; Anghel, D. F.; Stanga, G.; Marcu, A., 2009, Surfactant-free emulsion polymerization of styrene in the presence of silycated montmorillonite. *Applied Clay Science* 45, 64-170.
- Imai, T. In *Dielectric Polymer Nanocomposites*; Nelson J.K.: Springer: New York, 2010, Chapter 3, 65-93.
- Itagaki, T.; Matsumura, A.; Kato, M.; Usuki, A.; Kuroda, K. J., 2001, Synthesis of a kaolinite-poly ( $\beta$ -alanine) intercalation compound. *Mater. Sci. Lett.*, 20, 1483-1484.
- Kim S., Palomino A. M., 2011, Factors influencing the synthesis of tunable clay-polymer nanocomposites using bentonite and polyacrylamide, *Appl. Clay Sci.* v. 51, p.491-498.
- Li H., Zhou S.-X., Youa B., Wu L.-M., 2006, Morphology evolution of poly(St-co-BUA)/silica nanocomposite particles synthesized by emulsion polymerization. *Chinese Journal of Polymer Science* 24, 323-331.
- Lin K.-J., Dai C.-A., Lin K.-F., 2009, Revisit to the formation mechanism of exfoliated montmorillonite/pmma nanocomposite latex through soap-free emulsion polymerization. *J. Polym. Sci., Part A: Polym. Chem.* 47, 459-466.
- Ma P. C., Zhang Y. 2014, Perspectives of carbon nanotubes/polymer nanocomposites for wind blade materials. *Renewable Sustainable Energy Rev.* 30, p. 651-660.
- Meneghetti P., Qutubuddin S., 2004, Synthesis of poly(methyl methacrylate) nanocomposites via emulsion polymerization using a zwitterionic surfactant. *Langmuir*, 20, 3424-3430.

- Neto, J. C. M., Botan, R., Lona, L. M. F., Neto, J. E.; Pippo, W. A., 2015, Polystyrene/kaolinite nanocomposite synthesis and characterization via in situ emulsion polymerization. *Polym. Bull.* 72, 387-404.
- Paul D. R., Robeson L. M., 2008, Polymer nanotechnology: Nanocomposites, *Polymer* 49, p. 3187-3204.
- Romero-Ibarra I.C., Bonilla-Blancas E., Sánchez-Solís A., Manero O., 2012, Influence of the morphology of barium sulfate nanofibers and nanospheres on the physical properties of polyurethane nanocomposites. *Eur. Polym. J.* 48, 670-676.
- Sun, D., Li Y., Zhang B., Pan X., 2010, Preparation and characterization of novel nanocomposites based on polyacrylonitrile/kaolinite. *Composites Science and Technology* 70, 981-988.
- Tiarks F., Landfester K., Antonietti M., 2001, Silica nanoparticles as surfactants and fillers for latexes made by miniemulsion polymerization. *Langmuir* 17, 5775-5780.
- Villanueva M. P., Cabedo L., Giménez E., Lagarón, J. M., Coates P. D., Kelly A. L., 2014, Study of the dispersion of nanoclays in a LDPE matrix using microscopy and in-process ultrasonic monitoring, *Polym. Test.* 28, 277-287.
- Wang, L., Xie, X.; Su, S.; Feng, J.; Wilkie C. A., 2010, A comparison of the fire retardancy of poly(methyl methacrylate) using montmorillonite, layered double hydroxide and kaolinite, *Degrad. Stab.*, 95, 572-578.
- Wang T., Wang M., Zhang Z., Ge X., Fang Y., 2006, Preparation of core (PBA/layered silicate)-shell (PS) structured complex via  $\gamma$ -ray radiation seeded emulsion polymerization. *Mater. Lett.*, 60, 2544-2548.
- Yilmaz, O., Cheaburu, C. N., Gülümser, G., Vasile C., 2012, Preparation of stable acrylate/montmorillonite nanocomposite latex via in situ batch emulsion polymerization: Effect of clay types, *Eur. Polym. J.* 48, 1683-1695.
- Yang J., Fan H., Bu Z., LI B.-G, 2009, Influence of clay and predispersion method on the structure and properties of polystyrene (PS)-clay nanocomposites. *Polym. Eng. Sci.*, [S.v.], 1939-1943.
- Zhang B., Y. Pan L. X., Jia X., Wang X., 2007, Intercalation of acrylic acid and sodium acrylate into kaolinite and their in situ polymerization. *J. Phys. Chem. Solids.* 68, 135-142.