

## MONOMERIC COMPLEX COMPOUND BASED ON ACRYLAMIDE

F.A. Khamdamova, O.S. Maksumova

Tashkent chemical-technological Institute Republic of Uzbekistan, Tashkent

Email: [omaksumovas@mail.ru](mailto:omaksumovas@mail.ru)

**Abstract:** Monomeric complex compounds based on acrylamide and copper chlorides have been synthesized. The reaction of interaction of acrylamide with copper chloride was carried out by heating in solutions, followed by washing and drying of the precipitated crystalline precipitates of monomeric salts. It has been established that monomeric complex salts are formed in a metal-acrylamide molar ratio of 1:4. The structure and composition of the synthesized crystalline monomeric salts were studied by IR and NMR spectroscopy, X-ray diffraction and elemental analyses. The copper content in the resulting complex compounds was 12,5-14,0%. It is shown that the complex compound based on acrylamide and copper has a high degree of crystallinity, consists of 12,63% amorphous and 87,37% crystalline structure. Tetradentate coordination of copper with acrylamide and O-chelation due to donor-acceptor bonds of the carboxyl group -  $[C_{12}H_{24}N_4O_4Zn]$  were identified. In the IR spectra of the synthesized monomeric complex salts, absorption bands characteristic of Cu-O bonds and a shift in the maxima of the functional groups of acrylamide appear.

**Keywords:** monomer, acrylamide, copper chloride, complex salts, coordination, carbonyl group.

### Introduction

Metal-containing polymers and copolymers have a number of unique properties: biological and catalytic activity, biocidal, electrical and magnetic properties, etc. [1, 2].

At present, three main methods for obtaining metal-containing polymers are described in the literature: 1) the interaction of linear polymers with metals; 2) the reaction of polycondensation of the corresponding precursors with the incorporation of a metal ion into the main chain; 3) reactions of (co)polymerization of metal-containing monomers [2]. Each of these methods has its own advantages and disadvantages. However, one of the promising methods in this area is the third one, i.e. synthesis of metal-containing monomers, which are convenient systems for studying the regularities of the radical polymerization process, since they contain a chemically bound metal atom capable of coordinating interaction with a macroradical and other components of the reaction system.

The results of the synthesis and study of metal-containing monomers and their polymerization are reflected in numerous works of Pomogailo A.D., Jardimalieva G.I., Savostyanova V.S. and others [3,12]. The paper considers methods for the synthesis of metal-containing monomers that differ in the type of bond between the metal and the organic part of the molecule; a classification of these monomers is given. The influence of the nature of the metal on the polymerization process and the properties of the resulting products, the fields of application of metal-containing polymers, and the technological aspects of the synthesis of metal-containing monomers have been studied. The classification of metal-

containing monomers takes into account the type of bond between the metal and the organic part of the monomer. Based on this, metal-containing monomers can be divided into the following main types: monomers with covalent, ionic, donor-acceptor, and  $\pi$ -bonds [3,5].

The authors chose unsaturated dicarboxylic acids as the base compound for the preparation of metal-containing monomers. [6]. They synthesized Co (II), Ni (II), Cu (II), Zn (II) Fe (II), Fe (III), Cr (III) maleates, fumarates, and itoconates in up to 95% yield. Other authors have synthesized iron(III) carboxylates with acrylic, crotonic, linoleic, methacrylic, oleic, and sorbic acids [7]. The paper presents generalized data on the synthesis and reactivity of metal-containing monomers based on mono- and dicarboxylic unsaturated acids, the identification of the kinetic patterns of their polymerization and thermal transformations, as well as the study of the main properties of the resulting products [8].

The authors synthesized nickel(II) salts with unsaturated monocarboxylic acids: acrylic, methacrylic, sorbic, 4-pentic, propiolic, crotonic, linoleic, and oleic acids, studied their thermal properties, and synthesized nickel-containing nanocomposites by controlled thermolysis of the resulting carboxylates [9,15]. Vinyl porphyrin complexes of palladium and cobalt have also been synthesized [16].

In recent years, the attention of many researchers has been attracted by metal chelate monomers (MCM), whose characteristic features are the presence of unsaturated bonds and a metal chelate cycle for obtaining polymers and copolymers with desired properties [17,19].

Chlorine-containing compounds of anthranilamide with cobalt, nickel, and copper were obtained in an ethanol solution [20]. Using elemental analysis, vibrational and electronic spectra, it was shown that the synthesized solid compounds have an octahedral structure.

The authors synthesized metal complexes of manganese(II), iron(II), and nickel(II) chlorides with acrylamide [21]. It is shown that in all three complexes the coordination geometries of the metal centers include tetragonally distorted octahedral structures with four O-donor acrylamide atoms bound in equatorial and two chloride ligands. This paper presents a review of the literature on the coordination chemistry of acrylamide with various transition metals [22]. A general review of the structure and possible ways of coordinating acrylamide is discussed and data are given on the synthesis and structure of nitrate and chloride complexes of acrylamide coordinating exclusively through carbonyl oxygen  $[\text{Co}(\text{AAM})_4(\text{H}_2\text{O})_2](\text{NO}_3)_2$ ,  $[\text{Cu}(\text{AAM})_4(\text{NO}_3)_2]$ ,  $[\text{Co}(\text{AAM})_4\text{Cl}_2]$ , and  $[\text{Co}(\text{AAM})_6][\text{CoCl}_4]$ .

The authors synthesized acrylamide complexes of cobalt: blue dichlorotetrakis(acrylamide)cobalt(II) (1) and pink (acrylamide)cobalt(II) tetrachlorocobaltate (2) [23]. They found that the coordination of CoII in 1 includes a tetragonally distorted octahedral structure with four O-donor acrylamide atoms in equatorial positions and two chloride ions in apical positions. The second complex 2 in ionic form contains  $\text{Co}^{+2}$  cations surrounded by an octahedral array of O-coordinated acrylamide ligands. In other works, the authors present the results of the synthesis, spectroscopy, and single-crystal X-ray structure of the acrylamide ligand N-pyrazolylpropanamide and its complexes with copper(II) and cobalt(II) chlorides [24]. The work presents comparative data of the crystal structure of acrylamide and complexes of acrylamide with metals formed with

divalent transition metal chlorides [25]. Also, the authors determined the structure of the synthesized acrylamide complexes of metal nitrates using single-crystal X-ray diffraction analysis [26]. It has been established that all synthesized complexes crystallize in the triclinic space group.

As can be seen, acrylamide has a high complexing ability and is an interesting type of ligand containing three donor atoms: the nitrogen atom of the amide group, the double bond between the carbon atoms and the oxygen of the carboxyl group.

**The aim of this work** is the targeted synthesis and study of the composition and structure of a metal-containing monomer without chloride ions with a MO-bond of the donor-acceptor type based on acrylamide with copper.

### **Experimental part.**

Acrylamide (2-propenamide)  $\text{CH}_2=\text{CHC}(\text{O})\text{NH}_2$  - acrylic acid amide, is a colorless crystals with  $T_{\text{melt.}}=84.5^\circ\text{C}$ ,  $T_{\text{boil.}}=215^\circ\text{C}$ , density  $1.122 \text{ g/cm}^3$ . Soluble in water, ethanol, acetone. Ethanol (ethyl alcohol, methylcarbinol) -  $\text{CH}_3\text{CH}_2\text{OH}$  - monohydric aliphatic alcohol, colorless, easily mobile liquid with a characteristic odor.  $T_{\text{m.}}=-114.15^\circ\text{C}$ ,  $T_{\text{boil.}}=78.39^\circ\text{C}$ , density  $0.7893 \text{ g/cm}^3$ . It was absolutized by dehydration with calcium oxide, then it was distilled and a fraction with  $T_{\text{bp}}$  was taken.  $= 78^\circ\text{C}$ . Copper chloride -  $\text{CuCl}_2$  is a bluish-green odorless crystals with  $T_{\text{melt}} = 498 \text{ oC}$ ;  $T_{\text{boil.}}=993 \text{ oC}$ ; density  $3.386 \text{ g/cm}^3$ .

The IR spectra of the starting reagents and the synthesized monomers were recorded on an IRTracer-100 IR-Fourier spectrophotometer developed by SHIMADZU (Japan) in the wavenumber range  $400\text{-}4000 \text{ cm}^{-1}$  in KBr tablets. The PMR spectra of the initial reagents and synthesized substances were recorded on a Varian-T-6- spectrometer with an operating frequency of  $60.0 \text{ MHz}$  on H nuclei at a temperature of  $30^\circ\text{C}$ . Sample preparation requires 5-10 mg of the substance. The solvent used should ideally not contain its own protons ( $\text{CD}_3\text{COCD}_3$ ). A small amount ( $\sim 1\%$ ) of TMS is also introduced into the ampoule as internal ethanol.

NMR spectra were recorded on an Avance 500 spectrometer (Bruker, Germany) with an operating frequency of  $500 \text{ MHz}$  for  $^1\text{H}$  nuclei and  $126 \text{ MHz}$  for  $^{13}\text{C}$  nuclei at a temperature of  $293 \text{ K}$ . The following parameters for recording  $^{13}\text{C}$  NMR spectra were used: sampling time for the decay of free induction (AQT =  $0,5 \text{ s}$ ); relaxation delay time (RD =  $2 \text{ s}$ ); number of savings (NS =  $22,000$ ); the number of points describing the real spectrum (SI= $32 \text{ K}$ ). The number of accumulations in recording  $^1\text{H}$  NMR spectra was  $128$ .

The structure of the synthesized acrylamide complex compounds was determined by X-ray diffraction analysis (XRD). Reflection sets were obtained at  $293 \text{ K}$  on Xcalibur R autodiffractometers (Oxford Diffraction, England). ( $\text{CuK}_\alpha$ -radiation,  $\lambda=1.54184 \text{ E}$ ,  $\omega$ -scanning, graphite monochromator). All non-hydrogen atoms were localized in difference syntheses of electron density and refined by F2hkl in the anisotropic approximation. The positions of all H atoms were calculated geometrically and included in the refinement in the isotropic approximation. The single crystal has the form of a thin transparent plate  $0,42 \times 0,12 \times 0,1 \text{ mm}$  in size.

Elemental analysis for carbon, hydrogen, and nitrogen was performed on a CHNS-3 FA 1108 Elemental Analyzer (Carlo Erba) automatic gas analyzer; for boron and manganese, by ICP MS on an iCAP 6300 Duo inductively coupled plasma atomic emission spectrometer.


Procedure for Synthesizing a Monomeric Complex Based on Acrylamide and  $\text{CuCl}_2$  Weighed 0,4 mol of acrylamide and 0,1 mol of  $\text{CuCl}_2$  salt were dissolved in 50 ml of ethanol and heated at  $60^\circ\text{C}$  for 5 hours. The mixture was then evaporated to 1/3 volume. After cooling to room temperature, a green crystalline precipitate formed. Chlorine ions were removed from the  $\text{AgNO}_3$  solution by precipitation. The resulting precipitate was filtered off, washed twice with acetone, and dried in air. The precipitate formed has the composition  $[\text{C}_{12}\text{H}_{24}\text{N}_4\text{O}_4\text{Cu}]$ .

### Discussion

A molecular complex compound based on acrylamide with copper chloride was synthesized at a reagent ratio of 4:1. The reaction of their addition can be described as follows:



The structure and composition of the resulting complex compound were confirmed by IR spectroscopy and elemental analysis (fig. 1,2).

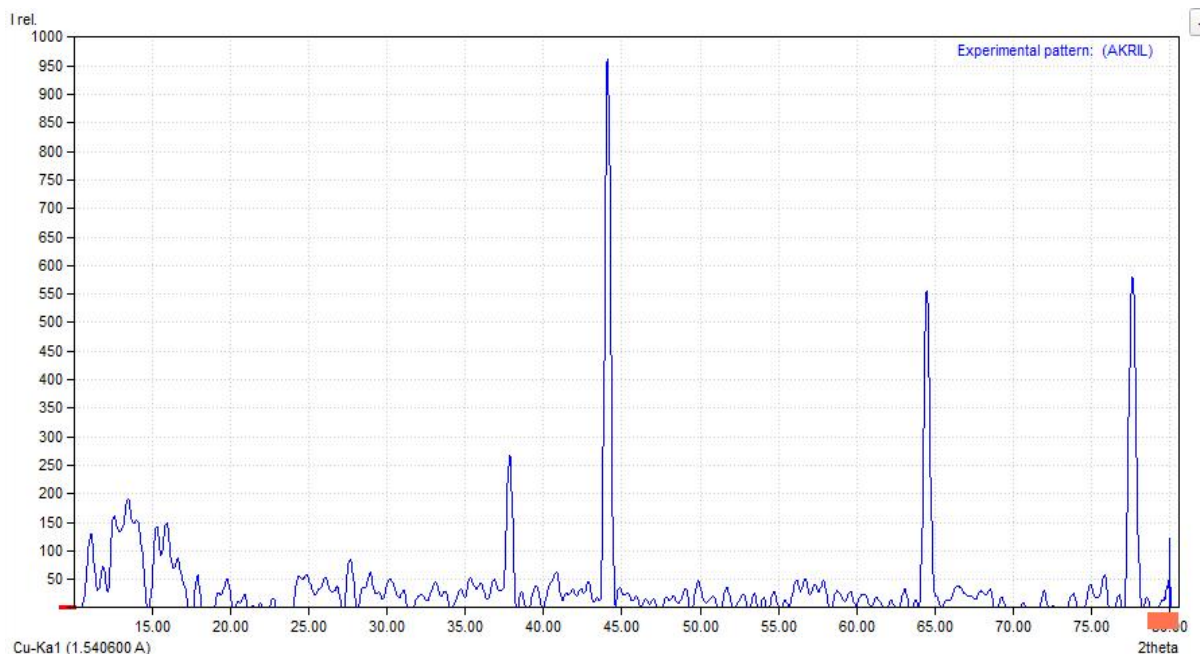


**Fig.1. Elemental composition of a monomeric complex compound based on acrylamide and copper(II).**

The synthesized complex compound of copper chloride with acrylamide is an air-stable green crystal having the following composition:

**Found (%): C - 41.10; H - 6.71; O -18.12; Cu -18.11; N-15.80;**

*Calculated (%): C- 41.00; H - 6.81; O -18.20; Cu-18.17; N-15.90*

The structure of the synthesized complex compound was established by the IR spectroscopic method from the shift of the characteristic absorption bands of acrylamide [27].

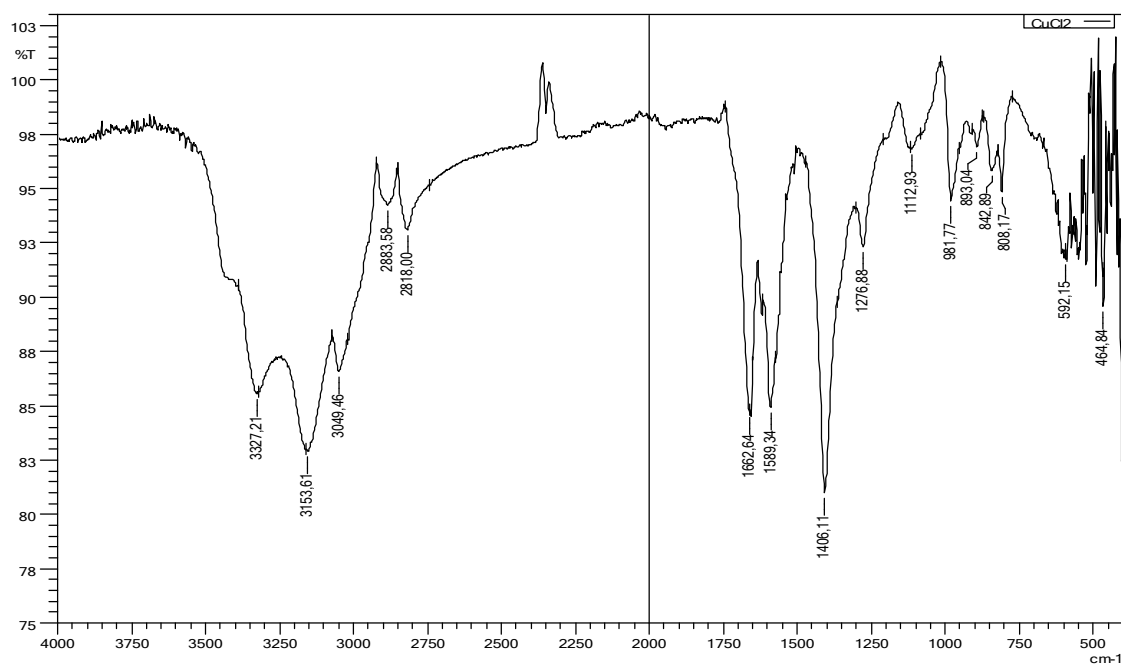

**Fig.2. IR spectrum of a monomeric complex compound based on acrylamide and copper(II).**

By comparing the IR spectra of free acrylamide and the complex compound, it was found that the strong broad band observed at  $1673\text{ cm}^{-1}$  in free acrylamide shifted during complexation to lower frequencies at  $1662\text{ cm}^{-1}$  (fig. 2). The absorption band of free acrylamide at  $1614\text{ cm}^{-1}$  shifted in the IR spectrum of the complex compound to lower wave numbers at  $1599\text{ cm}^{-1}$ . The absorption band of the  $\text{NH}_2$  group at  $1138\text{ cm}^{-1}$  in free acrylamide shifted to  $1112\text{ cm}^{-1}$ ;  $\text{C}=\text{C}$  absorption bands in the region of  $981\text{ cm}^{-1}$  and  $1276\text{ cm}^{-1}$ , characteristic of the region of out-of-plane bending vibrations  $=\text{CH}$ , and  $\text{C}=\text{C}$  stretching vibration bands in the region of  $1589\text{ cm}^{-1}$  show the preservation of double bonds. The results of IR spectroscopy show that the acrylamide ligands are bound to the complexing agent through the oxygen atoms of the carbonyl groups.

The results obtained show that the acrylamide ligands are bound to the complexing agent through the oxygen atoms of the carbonyl groups.

Also, the structure of the monomeric complex compound based on acrylamide and copper(II) was studied by  $^{13}\text{C}$  NMR and  $^1\text{H}$  PMR spectroscopy (fig. 3,4). It is known that, due to the presence of an unpaired electron, the copper(II) cation has paramagnetic properties [28]. It can be seen that in the  $^{13}\text{C}$  NMR spectra of solutions of copper(II) ions with acrylamide and a number of carbon signals with shifts from 35 to 180 ppm are observed. Broadened signals corresponding to carbon atoms of carboxyl groups are in the

region of 180 ppm. Such a shift and broadening of the signal of the carbon atom suggests participation in the donor-acceptor coordination of the carboxyl groups of acrylamide with copper (II) ions.

In the  $^1\text{H}$  NMR spectrum of a solution of acrylamide and copper(II) in a molar ratio of 4:1, a chemical shift of the signals of the hydrogen atoms of the methylene groups is observed in the range of 3.5-3.6 ppm. and broadening of these signals (Fig. 4). This phenomenon confirms the assumption that acrylamide carboxyl groups are involved in the coordination.

Also, the structure of the synthesized compound was studied by X-ray diffraction analysis (XRD) (table-1, Fig. 5).

According to X-ray diffraction data, in the crystal lattice of the complex compound based on acrylamide and copper(II), coordination of oxygen atoms  $-\text{C}=\text{O}$  of acrylamide fragments to the metal center is observed; one copper atom in the complex is bonded to four acrylamide molecules, and the coordination geometries of metal centers have a tetragonal structure with four O-donor acrylamide atoms [29–31]. It can be seen that the carbonyl groups of acrylamide c are bound to the copper atom and the double bond is not involved in the coordination (Fig. 5).

Khasanov\_XM-4  
13C\_D2O+Acetone\_08062021\_400 MHz

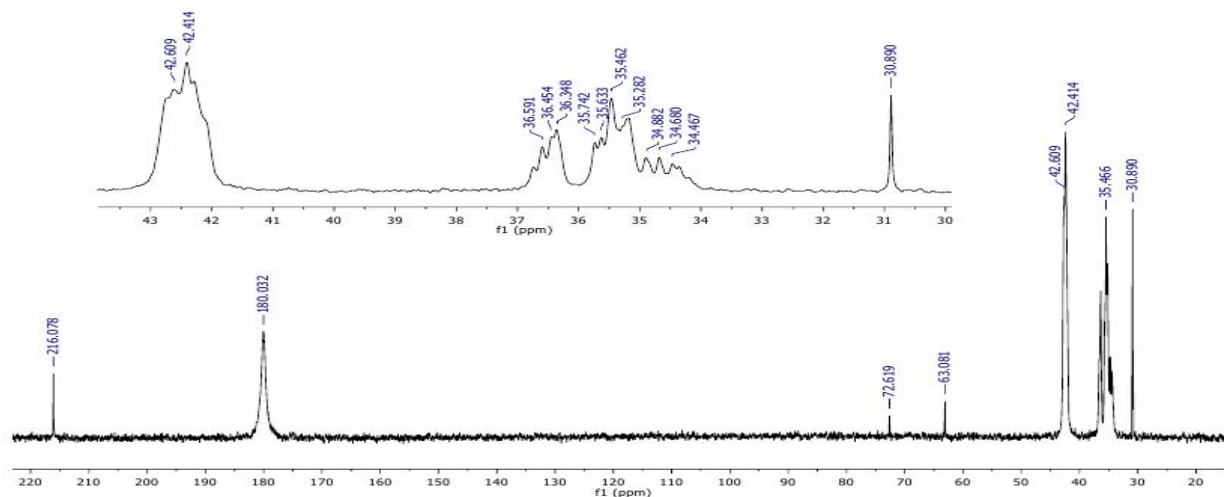


Fig.3.  $^{13}\text{C}$  NMR spectrum of a monomeric complex compound based on acrylamide and copper (II).

Khasanov\_XM-3  
 1H\_D2O+Acetone\_07062021\_400 MHz

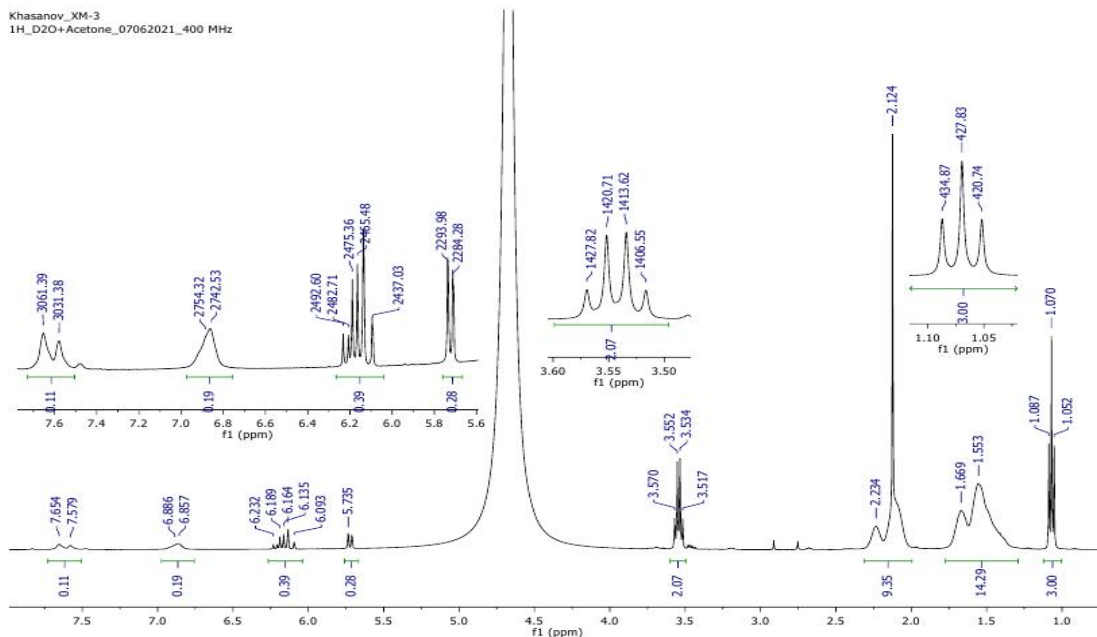


Fig.4. <sup>1</sup>H PMR spectrum of a monomeric complex compound based on acrylamide and copper (II).

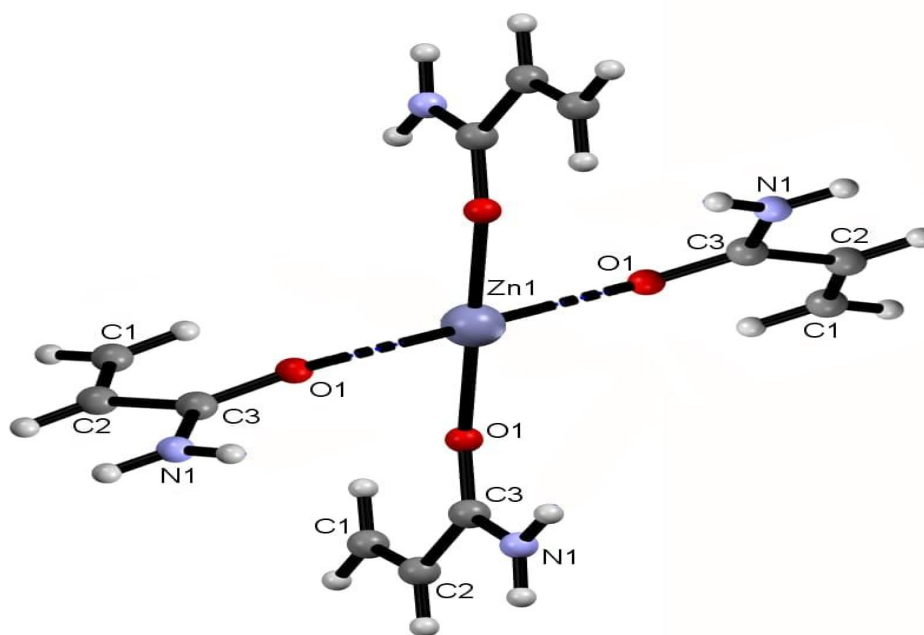


Fig.5. Molecular structure of a complex compound based on acrylamide and copper (II).

Table 1. Main crystallographic data and results of refinement of the structure of the synthesized complex

Molecular formula	C <sub>6</sub> H <sub>10</sub> C <sub>12</sub> N <sub>2</sub> O <sub>2</sub> Cu
M, g/mol	278,43
Syngony	Monoclinic
Spatial group	P2 <sub>1</sub> /s
Z	2
a, Å	3,7758 (4)
b, Å	12,4572 (14)
c, Å	10,8582 (13)
β(°)	92,296 (11)
V, Å <sup>3</sup>	510,32 (10)
d, g/sm <sup>3</sup>	1,812
Crystal sizes (mm)	0,03
Scan area, θ(°)	5,4 – 70,7
μ, mm <sup>-1</sup>	7,94
Total number of reflections	944
Number of reflections s I>2 σ (I)	785
R1 (I>2σ(I) and general)	0,084 (0,094)
wR2	0,25 (0,26)
COOF	1,14
Difference Peaks IP, e Å <sup>-3</sup>	1,68 и – 1,29


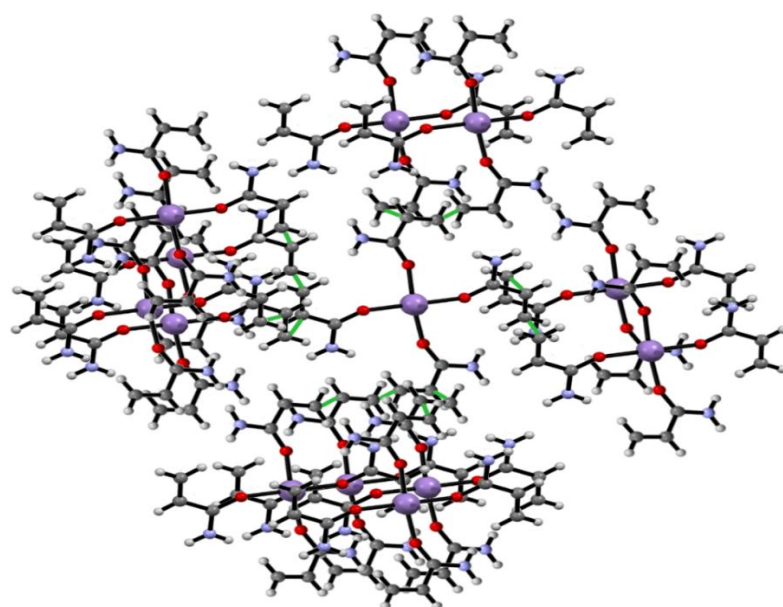


Fig.6. Crystal packing of molecules of a complex compound based on acrylamide and copper(II) in a unit cell.

a)

b)

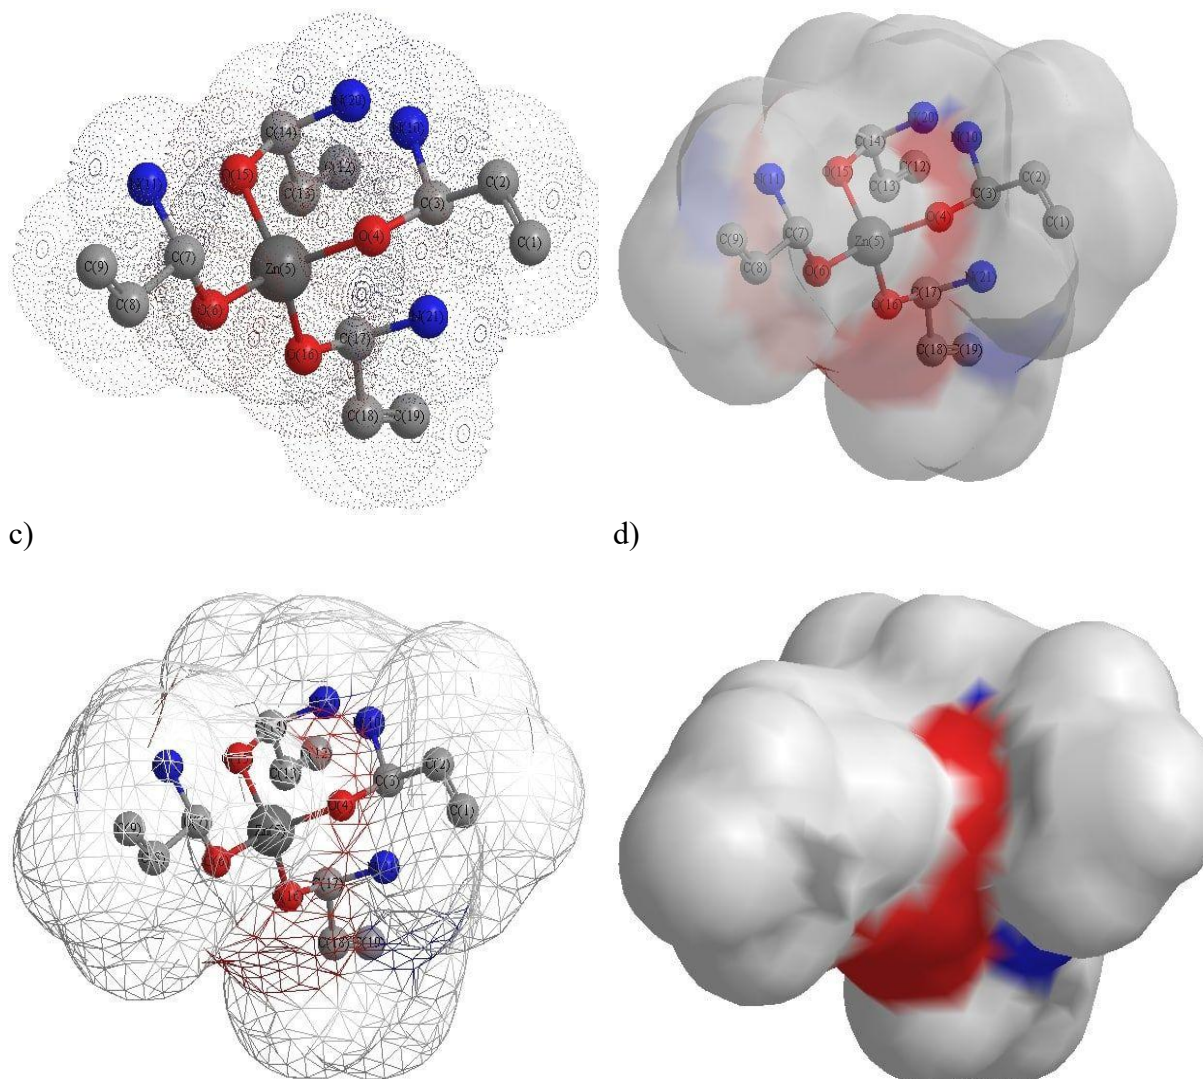

**Fig.7. a) and b) - Electron density distribution over atom of a complex compound based on acrylamide and copper(II); c) and d) - Electron density surface in a molecule of a complex compound based on acrylamide and copper (II).**

### Conclusion

Monomeric complex compounds based on acrylamide and Cu (II) were synthesized at a ratio of 4:1. The composition and structure of the synthesized monomers were established using elemental analysis, IR spectroscopy, and X-ray diffraction analysis.

It is shown that the complex compound based on acrylamide and copper has a high degree of crystallinity, consists of 12,63% amorphous and 87,37% crystalline structure.

X-ray diffraction analysis has shown that in the crystal lattice of the complex compound based on acrylamide and copper(II) the coordination of oxygen atoms  $-C=O$  of acrylamide fragments to the metal center is observed; tetra dentate coordination of copper with acrylamide and O-chelation due to donor-acceptor bonds of the carbonyl group with the formation of  $[C_{12}H_{24}N_4O_4Cu]$  were identified.

## References

1. Plate N.A., Slivinsky E.V. Fundamentals of chemistry and technology of monomers. M.: Nauka: MAIK "Nauka/Interperiodika", 2002. -696 p.
2. Pomogailo A.D., Savost'yanov V.S. Metal-containing monomers and polymers based on them. M.: Chemistry, 1988. - 384 p.
3. Pomogailo A.D., Savost'yanov V.S., Dzhardimalieva G.I., Dubovitsky A.V., Ponomarev A.N. //Izv. RAS Ser. chem. 1995. No. 6. -WITH. 1096.
4. Barelko V.V., Pomogailo A.D., Dzhardimalieva G.I., Evstratova S.I., Rozenberg A.S. // Dokl.RAN, 1999. -T. 365. No. 2. -S. 201.
5. Rozenberg A.S., Raevsky A.V., Alexandrova E.I., Kolesova O.I., Dzhardimalieva G.I., Pomogailo A.D. // Izv. RAS Ser. chem. 2001. No. 5. -WITH. 862.
6. Porollo (Ivleva) N.P., Aliev Z.G., Dzhardimalieva G.I., Ivleva I.N., Uflyand I.E., Pomogailo A.D., Ovanesyanyan N.S. Preparation and reactivity of metal-containing monomers. Message 47. Synthesis and structure of salts of unsaturated dicarboxylic acids // Izv. RAN. ser. chem. -1996. - No. 12. - S.375-382.
7. A.S. Pronin, S.A. Semenov, D.B. Drobot, G.I. Jardimalieva. Synthesis and thermal transformations of unsaturated iron(III) monocarboxylates as precursors of metal-polymer nanocomposites // Journal of Inorganic Chemistry, 2018. Volume 63. -P. 1005-1014.
8. Gulzhian Dzhardimalieva, Anatoly Pomogailo. Monomeric and polymeric metal carboxylates. Publishing house: FIZMATLIT, 2009. -400 p.
9. G. I. Dzhardimalieva, A. O. Tonoyan, A. D. Pomogailo, S. P. Davtyan. Preparation and reactivity of metal-containing monomers. Communication 6. Polymerization of metal monomers based on alkoxy derivatives of Ti(IV) and some properties of the resulting products // Izv. USSR Academy of Sciences, ser. chem. 1987. No. 8. -C. 1744-1748.
10. M.R. Muidinov, G.I. Jardimalieva, B.S. Selenova, A.D. Pomogailo, I.M. Barkalov. Preparation and reactivity of metal-containing monomers. Communication 9. Low-temperature postradiation polymerization of metal-containing monomers during devitrification of matrices // Izv. USSR Academy of Sciences, ser. chem. 1988. -S. 2507-2511.
11. G.I. Dzhardimalieva, A.D. Pomogailo, S.P. Davtyan, V.I. Ponomarev. Preparation and reactivity of metal-containing monomers. Message 8. Polymerization of transition metal acrylates // Izv. USSR Academy of Sciences, ser. chem. 1988. No. 7. -C. 1531-1536.
12. N.N. Smirnova, T.A. Bykova, V.N. Larina, T.G. Kulagina, A.D. Pomogailo, G.I. Dzhardimalieva. Thermodynamic properties of hydrated acrylamide and polyacrylamide complexes of cobalt nitrate in the range from T - 0 to 380 K // High-molecular compounds, series A, 2010, volume 52, no. 4. -S. 547-553.
13. Semenov S.A., Drobot D.V., Musatova V.Yu., Pronin A.S., Pomogailo A.D., Dzhardimalieva G.I., Popenko V.I. Synthesis and thermal transformations of unsaturated dicarboxylates of cobalt (II) - precursors of metal-polymer nanocomposites // Journal of Inorganic Chemistry. 2015. V. 60. No. 8. -S. 991.
14. Pomogailo A.D., Dzhardimalieva G.I., Pomogailo S.I., Golubeva N.D., Shilov G.V., Javadyan E.A., Burlov A.S., Mashchenko S.A., Garnovsky D.BUT. Obtaining and reactivity of metal-containing monomers and nanostructured materials obtained by controlled thermolysis of azomethine chelate Ni, Co and Cu metal complexes // Izvestia of the Academy of Sciences. Chemical series. 2016. No. 1. -S. 139-150.

15. A.S. Pronin, S.A. Semenov, D.V. Drobot, E.V. Volchkova, G.I. Dzhardimalieva. Synthesis and thermal transformations of nickel(II) carboxylates with anions of unsaturated monocarboxylic acids - precursors of metal-containing nanocomposites // *Journal of Inorganic Chemistry*, 2020, vol. 65, no. 8. –p. 1061–1072.
16. Berezovsky V.V., Werle D., Tsareva O., Makarov G., Pomogailo S.I., Glagolev N.N., Zhilina Z.I., Voloshanovsky I.S., Roshchupkin V.P., Pomogailo A.D. Preparation and reactivity of metal-containing monomers. *Message 64. Synthesis, structure, polymerization transformations and catalytic properties of vinyl-porphyrin complexes of palladium and cobalt* // *Izvestiya Akademii Nauk. Chemical series*, 2007. No. 1. -S. 152-158.
17. Uflyand, I.E. New Example of Metal-Containing Monomers for Frontal Polymerization // I.E. Uflyand, V.A. Zhinzhiro, G.I. Dzhardimalieva // *ChemistrySelect*. -2019. -V.4. -N7. -P.2105-2108.
18. Jardimalieva G.I. Zharmagambetova A.K., Kudaibergenov S.U., Uflyand I.E. Polymer-immobilized clusters and nanoparticles of metals in catalysis // *Kinetics and catalysis*, 2020. -V.61, No. 2. -WITH. 195-224.
19. Wöhrle D., Pomogaylo A.D., *Metal Complexes and Metal in Makromoleculs – Synthesis, Structure and properties*. Weinheim, Berlin: Wiley-VCH, 2003.
20. N. N. Smirnova, T. A. Bykova, V. N. Larina, T. G. Kulagina, A. D. Pomogailo, G. I. Dzhardimalieva. Thermodynamic properties of hydrated acrylamide and polyacrylamide complexes of cobalt nitrate in the range from T 0 to 380 K // *Vysokomolekular Compounds, Serie A*, 2010, vol. 52, no. 4. –S. 547-553.
21. J.R.Allan, B.McCloy, A.D.Paton, W.E.Smith, D.L.Gerrard. Thermal, structural and electrical studies of the chloro complexes of cobalt, nickel and copper with anthranilamide // *Thermochimica Acta*, 1992. Volume 205, Pages 127-137.
22. K. B. Girma, Volker Lorenz, Steffen Blaurock, Frank T. Edelmann. Coordination Chemistry of Acrylamide: 1. Cobalt(II) Chloride Complexes with Acrylamide – Synthesis and Crystal Structures // *Journal of Inorganic and General chemistry*. Volume 631, Issue 13-14 October 2005. Pages 2763-2769.
23. Girma K.B., Lorenz V., Blaurock S., Edelmann F.T. Coordination chemistry of acrylamide // *Coordination Chemistry Reviews*. Volume 249, Issues 11–12, June 2005, Pages 1283-1293.
24. K.B Girma, Volker Lorenz, Steffen Blaurock, Frank T Edelmann. Coordination Chemistry of Acrylamide 1. Cobalt(II) Chloride Complexes with Acrylamide Synthesis and Crystal Structures // *Zeitschrift für anorganische und allgemeine Chemie*, 2005, № 8, Volume 631, Pages 1419-1422.
25. K. B Girma, V.Lorenz, S.Blaurock, F.T.Edelmann. Coordination Chemistry of Acrylamide. 6 Synthesis and Coordination Compounds of N-Pyrazolylpropanamide – a Versatile Acrylamide-derived Ligand // *Zeitschrift für anorganische und allgemeine Chemie*. 2008/2. 634 (2). Pages 267-273.
26. KB Girma, Volker Lorenz, Steffen Blaurock, Frank T. Edelmann. Coordination chemistry of acrylamide 3: Synthesis, crystal structure and IR spectroscopic properties of dichlorotetrakis (O-acrylamide) copper (II), [Cu(O-OC(NH<sub>2</sub>) CHCH<sub>2</sub>)<sub>4</sub>Cl<sub>2</sub>] // *Inorganica chimica acta*. 2006/1/1. 359. Pages 364-368.
27. Nakanishi K. *Infrared spectra and structure of organic compounds*. – M.: Mir. 1965.– 233 p.
28. Martell A.E., Hancock R.D. *Metal complexes in aqueous solutions*. Berlin: Springer, 1996. -254 p.

29. Elshenbroich K. Organometallic chemistry [Electronic resource] per. with him. - 2nd ed. (el.). — M.: BINOM. Knowledge Laboratory, 2014. - 746 p.
30. S.I. Evstratova, G.V. Shilov, G.I. Jardimalieva, A.D. Pomogailo, I.E. Uflyand, S.M. Aldoshin. Synthesis and crystal structure of the acrylamide complex of copper (II) nitrate // Koord. chemistry. 2001. V. 27. No. 10. S. 778-780.
31. Steed, J. V. Supramolecular Chemistry: [transl. from English] / J.V. Steed, J.L. Atwood. - M.: ICC Akademkniga, 2007. T. 1-2. – 895 p.