



## ACCEPTED MANUSCRIPT

This is an early electronic version of an as-received manuscript that has been accepted for publication in the Journal of the Serbian Chemical Society but has not yet been subjected to the editing process and publishing procedure applied by the JSCS Editorial Office.

Please cite this article as L. Todan, D. C. Culita, M. E. Soare, R. M. Ion, R. C. Fierascu and M. Maganu, *J. Serb. Chem. Soc.* (2023) <https://doi.org/10.2298/JSC221028010T>

This “raw” version of the manuscript is being provided to the authors and readers for their technical service. It must be stressed that the manuscript still has to be subjected to copyediting, typesetting, English grammar and syntax corrections, professional editing and authors’ review of the galley proof before it is published in its final form. Please note that during these publishing processes, many errors may emerge which could affect the final content of the manuscript and all legal disclaimers applied according to the policies of the Journal.





*J. Serb. Chem. Soc.* **00(0)**1-12 (2022)  
JSCS-12113

## Immobilization of natural betalain pigments in inorganic hosts

LIGIA TODAN<sup>1\*</sup> DANIELA C CULITA<sup>1</sup>, MIRABELA E. SOARE<sup>1</sup>, RODICA M. ION<sup>2</sup>,  
RADU C. FIERASCU<sup>2</sup> AND MARIA MAGANU<sup>3</sup>

<sup>1</sup>Ilie Murgulescu Institute of Physical Chemistry, Romanian Academy, 202 Splaiul  
Independentei, 060021 Bucharest, Romania, <sup>2</sup>National Institute for Research & Development in  
Chemistry and Petrochemistry-ICECHIM, 202 Splaiul Independentei, 060021 Bucharest,  
Romania, and <sup>3</sup>„Costin D. Nenitescu” Institute of Organic and Supramolecular Chemistry,  
Romanian Academy, 202 B Splaiul Independentei, 060023 Bucharest, Romania

(Received 28 October 2022; Revised 21 January 2023; Accepted 1 March 2023)

**Abstract:** In search of new food-grade pH sensitive formulations, red beet extract rich in betacyanin was included in different inorganic matrices based on silica and aluminosilicate to improve the stability of the dye. By the direct method of encapsulation of the pigments in silica support, stabilizing agents such as inclusion complex forming  $\beta$ -cyclodextrin and ascorbic acid were added. The post loading system assumes the synthesis of porous silica and aluminosilicate powders and the adsorption of the beet extract by these supports. The unloaded carriers were structurally and texturally characterized (X-ray diffraction, FTIR, N<sub>2</sub>-physisorption). The presence of betanin, approved as a red food colorant, was evidenced by UV-vis spectroscopy in all the hosts. Color properties were investigated as well as the pH generated color variations of the powders exposed to ammonia in the head-space of a sealed vessel. The obtained results could widen the field of applications of beet extract, the prepared ecological formulations could provide added value to edible products packaging.

**Keywords:** betanin; encapsulation; mesoporous silica; aluminosilicate; color parameters

### INTRODUCTION

Betalains are the major pigments abundantly found in beetroot (*Beta vulgaris*) which are chemically defined as the derivatives of betalamic acid.<sup>1</sup> Betalains can be divided into yellow-orange betaxanthins and red-violet betacyanins. Of the betalains, betanin is approved for use as colorant in food industry (E number E162, CI Natural Red 33) and is considered a better choice than chemically synthesized pigments. It has commercial applications for foodstuff, cosmetics, and pharmaceuticals.<sup>2</sup> Betanin is almost totally extracted from beetroot crops and sold

\*Corresponding author E-mail: [l\\_todan@yahoo.co.uk](mailto:l_todan@yahoo.co.uk)  
<https://doi.org/10.2298/JSC221028010T>

as beetroot extract.<sup>3</sup> All betalains are water soluble. The main factors influencing their stability are light, oxygen concentration, temperature, the presence of water, and pH. They retain their tinctorial strength and color shade over a pH range of 3 - 7.<sup>1,2</sup> The fact that betacyanins show sensitivity to pH makes them suitable for use as colorimetric indicators for detecting changes of the environment especially in case of edible products, improving thus the protection and shelf life of foodstuffs or pharmaceuticals.<sup>4</sup> To preserve the chemical structure of the pigment and to facilitate its use in commercial applications, different ways of stabilization were used. Metal-chelates formation, cyclodextrin complexes, addition of organic acids, inclusion in different matrices should be mentioned.<sup>5,6</sup> It was shown that cyclodextrins are promising stabilizing agents of betalain molecules,  $\beta$ -cyclodextrin ( $\beta$ -CD) forming an inclusion complex with betanin.<sup>5,6</sup> Copigmentation was used to preserve betalains color intensity and stability. It involves interactions between the dyes and other naturally occurring compounds such as ascorbic or citric acid which can be neutralizing agents for the electrophilic center of betalains.<sup>5,6</sup>

Immobilization of the beet pigments on a solid carrier, organic or inorganic, is a promising approach for improving the properties of the plant derived pigments, enabling thus the inclusion of certain additives that can confer better functionality to encapsulated betalain pigments. A wide range of encapsulation systems have been designed: natural products derived nanocarriers (maltodextrin, caseins), lipid-based nanocarriers, biopolymers based nanocarriers (chitosan, proteins), and inorganic carriers (carbon nanotubes, clay minerals,  $\gamma$ -alumina).<sup>6-8</sup> Two approaches for the inclusion of drugs into silica based particles of matrix type have been mentioned, namely direct drug encapsulation when the drug is dissolved in the liquid precursor prior to formation of the matrix and indirect encapsulation or post loading when carrier particles are first synthesized followed by encapsulation of the drug.<sup>9,10</sup>

The purpose of the present work was to obtain formulations betalains-SiO<sub>2</sub> and betalains-aluminosilicate, respectively, and to explore the two above mentioned loading modes of beet pigments into the silica-based carriers. Our results provide novel information about the structure and properties of the final hybrid pigments, especially the color response toward ammonia, a marker of food spoilage, the obtained data contributing to the development of product formulations which can favour the properties of food packaging.

## EXPERIMENTAL

### *Materials*

Ludox®SM-30 colloidal silica (30 wt. % suspension in water) and sodium hydroxide were from Sigma Aldrich.  $\beta$ -cyclodextrine was purchased from Wacker-Chemie GmbH. Ascorbic

acid pharmaceutical grade was purchased from Intra-Laboratories, cetyltrimethylammonium bromide (CTAB) from Carl Roth, aluminium oxide from Merck Millipore, sodium dodecyl sulfate (SDS) analytical grade from Applichem. The concentrated beetroot juice (100 %, Biotta food grade) produced by extraction of pigments from red beet and its subsequent pasteurization, with betanin the major coloring principle was used as natural dye.

#### *Characterization*

X-ray diffraction (XRD) analyses were performed using a 9 kW Rigaku SmartLab diffractometer (Rigaku Corp., Tokyo, Japan, operated at 45 kV and 200 mA, CuK $\alpha$  radiation  $\lambda$  = 1.54059 Å), in scanning mode 2 $\theta$ / $\theta$ , between 2 and 90° (2 $\theta$ ) for wide-angle analysis and between 0.05 and 8° (2 $\theta$ ) for small angle analysis, measuring scan step 0.02°, scan speed 8° min<sup>-1</sup> (wide angle) and 4° min<sup>-1</sup> (small angle). Components were identified by comparison with ICDD data. FT-IR spectra were recorded on a Bruker Vertex 70 Spectrometer with horizontal device for attenuated reflectance and diamond crystal, on a spectral window ranging from 4000 to 400 cm<sup>-1</sup>, at a spectral resolution of 2 cm<sup>-1</sup>. Spectra were recorded without any sample preparation and were processed with OPUS 5.5 program (Bruker). Nitrogen adsorption-desorption isotherms at 77K were recorded on a Micromeritics ASAP 2020 automated gas adsorption system (Norcross, GA, USA). The samples were degassed at 250 °C for 4 h under vacuum before analysis. Specific surface areas ( $S_{\text{BET}}$ ) were calculated according to the Brunauer-Emmett-Teller (BET) equation, using adsorption data in the relative pressure range between 0.05 and 0.30. The total pore volume ( $V_{\text{total}}$ ) was estimated from the amount adsorbed at the relative pressure of 0.99. The pore size distribution curves were obtained from the desorption data using the Barrett-Joyner-Halenda (BJH) model. UV-Vis spectra were recorded using a JASCO V-750 spectrophotometer equipped with an integrating sphere that allows measurements on solid samples. Chromatic parameters were registered with a Konica Minolta CR-410 colorimeter with a white calibration plate ( $Y=94.27$ ,  $x=-1.06$ ,  $y=3.45$ ), measurements were done in triplicate and means reported. In the CIE L\*a\*b\* uniform color space the color coordinates are: L\* (brightness), a\* (green-red) chromaticity, b\* (blue-yellow) chromaticity to describe the color of the matrices.<sup>11</sup>

#### *Preparation*

The two approaches mentioned above were used to include beet extract into the carriers. In the direct encapsulation procedure, an aqueous mixture of 5 ml beet juice and 0.1 g  $\beta$ -CD is added, under constant stirring and room temperature, to 20 ml colloidal silica which was previously diluted with 12 ml water and brought to a pH of ~ 4 with an ascorbic acid solution of 15 %. Then the dye containing composition was introduced in a vacuum rotary evaporator and kept at 30 °C under vacuum until the liquid was evaporated and the precipitate was separated and crushed into powder. It was denoted silica-bet 1.

Two mesoporous supports were prepared for beet juice adsorption. One of them, silica 2, was obtained from colloidal silica and CTAB as template agent, the molar ratio SiO<sub>2</sub>/CTAB being equal to 0.12/0.3 10<sup>-3</sup>. The mixture was brought to an acid pH with an acetic acid solution 20 %, under stirring and kept for 5 days at room temperature. The other one, an aluminosilicate carrier (silicaAl 3) is obtained by a hydrothermal process (90 °C, 48 h) in a basic medium from colloidal silica and Na<sub>2</sub>O·Al<sub>2</sub>O<sub>3</sub> using SDS as a structure directing surfactant. The molar ratios of the components were SiO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> = 6, SiO<sub>2</sub> /Na<sub>2</sub>O = 10/7, SiO<sub>2</sub>/SDS = 10/1.4. The silica 2 and silicaAl 3 powders were separated by repeated centrifugation and washing with distilled

water and then they were thermally treated at 600 °C, with 5 h plateau and a heating rate of 1 °C min<sup>-1</sup>. 0.8 g of each host material was mixed with 1.2 ml beet juice, stirred for homogenization and followed by 5 h vacuum drying in dark conditions. A colored powder was obtained.

Equal quantities of the three dye loaded powders were spread on plates and were put in a PET container together with a Petri dish containing ammonium hydroxide solution 25 %. The container was sealed for about 15 min so that the powders should be in contact with the ammonium vapours developed into the headspace. The color changes were determined.

## RESULTS AND DISCUSSION

### *Structural characterization of the unloaded matrices*

#### *X-ray diffraction*

The crystallographic structure of the as prepared samples was evaluated by XRD analysis. The diffraction patterns of the powders are presented in Fig. 1. As can be seen in Fig. 1 a, the diffraction patterns indicate that the silica carrier is amorphous, marked by the existence of a broad peak at  $2\theta$  in the range 20-35° attributed to amorphous silica.<sup>12</sup> The pattern of the aluminosilicate sample in Fig. 1 b shows the formation of a crystalline phase of the zeolite Y type (identification was performed using PDXL software from Rigaku connected to ICDD database).

The inset of Fig. 1 a shows the SAXS diagram of the two as prepared powders. The variation of the scattering intensities with the scattering vector ( $q$ ) is due to the electron density difference between the matrices and the empty pores.<sup>13,14</sup> The scattering curves of each of the two samples present a regular structure, confirming the long-range well-ordered mesostructured.<sup>15,16</sup>

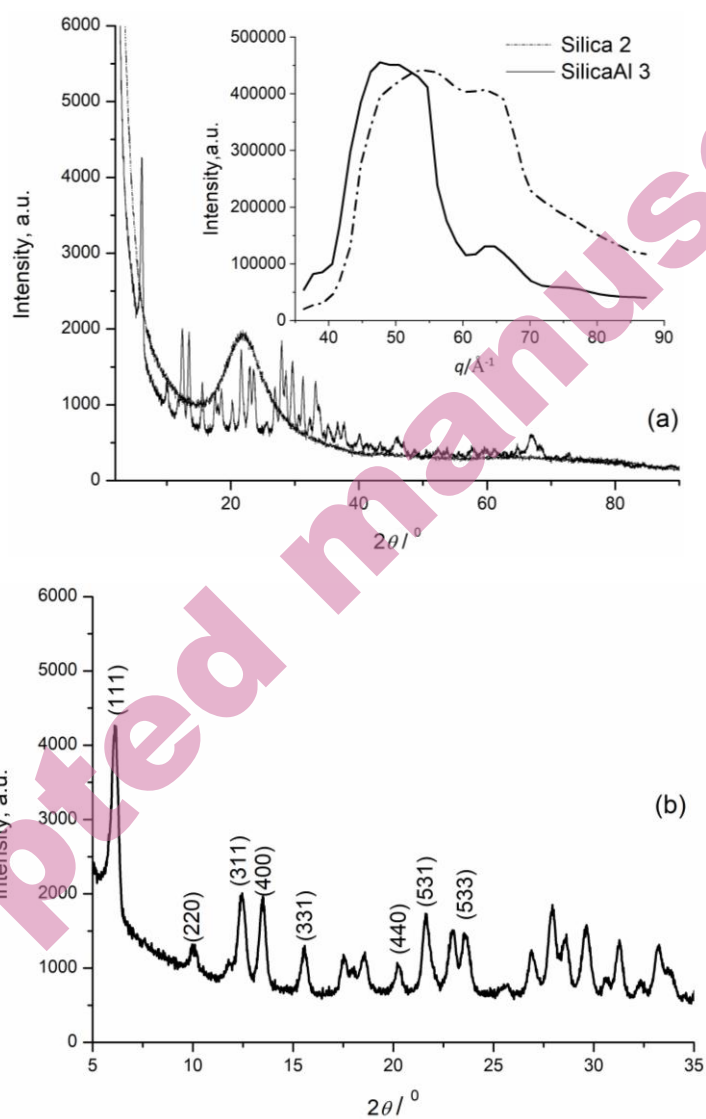


Fig. 1. XRD patterns of Silica 2 and silicaAl 3 (the inset shows SAXS diagram of the same unloaded carriers) (a) and details of crystal structure of silicaAl 3 (b)

#### *N<sub>2</sub> physisorption*

In Fig.2 one can see that both samples show type IV isotherms according to IUPAC classification, typical for mesoporous materials.

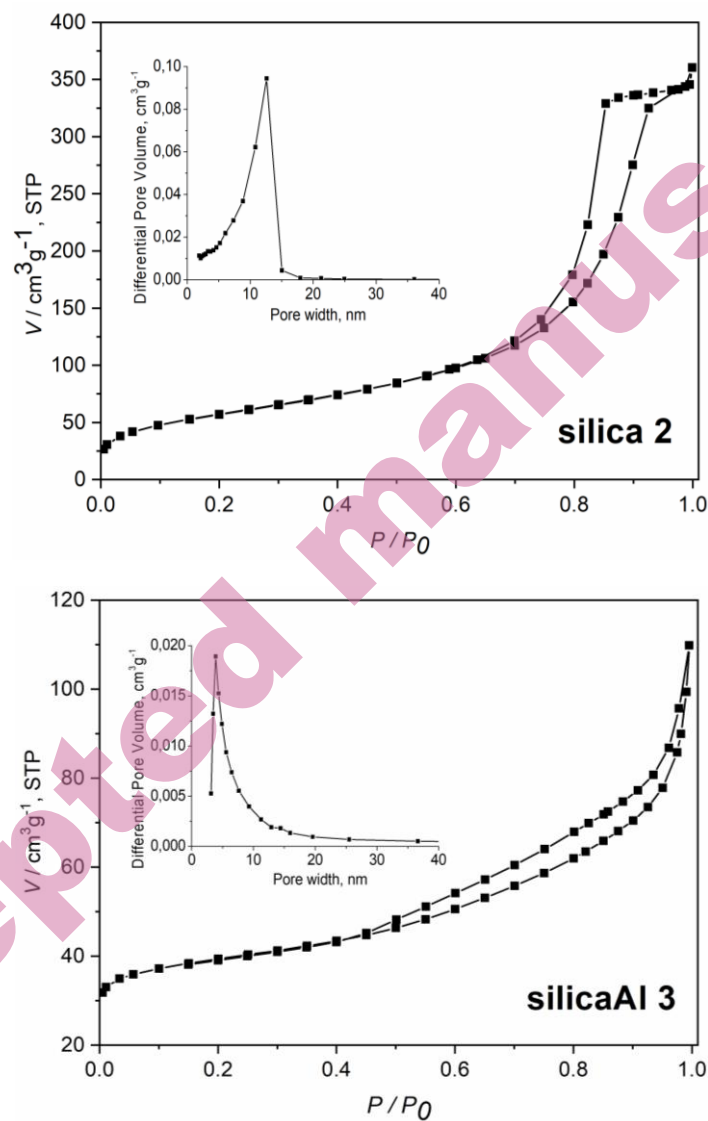


Fig. 2. N<sub>2</sub> adsorption–desorption isotherms and pore size distributions (inset of the figures) of silica 2 and silicaAl 3 supports

Silica 2 support exhibits a H2 hysteresis loop that indicate the existence of a complex pore structure in which network effects are important. In the case of silicaAl 3 support, the hysteresis loop is of H3 type suggesting an assemblage of slit-shaped pores. The pore size distribution graphs show a unimodal distribution



for both types of supports with peak maxima at 12.6 nm for silica and 3.8 nm for aluminosilicate. A t-plot analysis indicated the absence of microporosity in the silica support, whereas in aluminosilicate an important fraction of micropores was detected (~70 %). BET surface area, as well as total pore volume are higher for silica type carrier than for zeolite-Y type aluminosilicate (Table I).

Table I. Textural parameters of silica 2 and silicaAl 3 supports

Sample	$S_{\text{BET}} / \text{m}^2 \text{g}^{-1}$	$V_{\text{total}} / \text{cm}^3 \text{g}^{-1}$
Silica 2	205.3	0.557
silicaAl3	148.5	0.138

Porosity measurements as well as the X-ray analysis prove that the supports are highly ordered materials.

#### *Infrared absorption spectra*

Fig. 3 shows the FTIR spectra of the unloaded matrices. The strongest absorption bands of the two samples lie in the wavenumbers range 1200-950  $\text{cm}^{-1}$  described as an asymmetric stretching mode O-(Si,Al)-O.<sup>17</sup> Silica 2 sample shows a peak at 1110  $\text{cm}^{-1}$  while silicaAl 3 at 986  $\text{cm}^{-1}$ , the presence of Al atoms in the structure generating a shift to lower wavenumbers.<sup>16</sup>

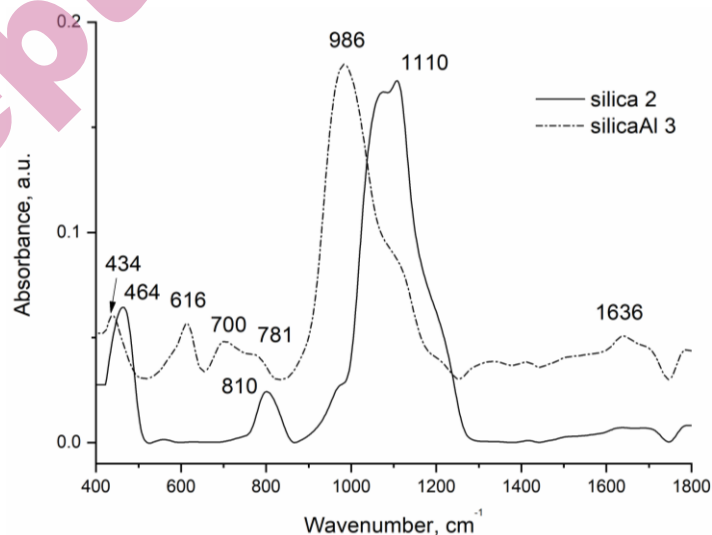


Fig 3. FTIR spectra of silica 2 and silicaAl 3 supports

In the region 420-500  $\text{cm}^{-1}$  the bands are assigned to O-(Si, Al)-O bending mode.<sup>17</sup> A strong sharp band can be seen in the spectrum of silica 2 matrix at 464  $\text{cm}^{-1}$ . In the aluminum containing one it is shifted to 434  $\text{cm}^{-1}$  and becomes weaker. Bands corresponding to symmetric stretching modes appear in the range 650-820  $\text{cm}^{-1}$ .<sup>17</sup> In the spectrum of the silica 2 sample a single band at 810  $\text{cm}^{-1}$  can be attributed to Si-O-Si sym stretching<sup>18</sup>, while the presence of Al in the sample generates a widening and flattening of the bands (781  $\text{cm}^{-1}$  and 700  $\text{cm}^{-1}$ ).<sup>18</sup> The absorption bands at 1636  $\text{cm}^{-1}$  show the presence of water in the matrices.<sup>12</sup>

FTIR spectra confirm the formation of an aluminosilicate type frame work in accordance with XRD results and show that the structure directing agent was removed by thermal treatment.

#### *Characterization of matrices loaded with beet juice pigment*

##### *UV-Vis spectroscopy of the dye-carrier formulation*

There is an electron resonance system based on the two nitrogen atoms of the betalains molecules which is linked to the colour properties.<sup>19</sup> Bethaxanthins with a more simple structure around nitrogen atom have a typical UV-vis absorption maximum in the 457-480 nm region and are yellow while the betacyanins with an extended resonance system generate wavelengths in the range 524-542 nm that makes them violet.<sup>19-22</sup>

Fig. 4 presents the UV-Vis spectra of the three prepared samples by inclusion and adsorption. All display the betanin absorption maximum (535 -543 nm). Compared to silica-bet 1 spectrum, in which case the pigments can be stabilized by inclusion complex formation with  $\beta$ -CD<sup>5</sup>, the silica 2 and silicaAl 3 samples have different profiles. In case of silica 2, an overlapping of the bands is observed in the 472-535 nm range and silicaAl 3 spectrum shows shifts to lower (415 nm) and higher values (543 nm). Betalains being known as electron donating compounds<sup>21</sup>, this fact can be due to interactions with the matrices which become more significant for a high specific surface area and micro/mesoporosity.<sup>23,24</sup> Aluminium coordinative unsaturated sites in the network of silicaAl 3 enhances the interactions with adsorbed betalains.<sup>8,24</sup>

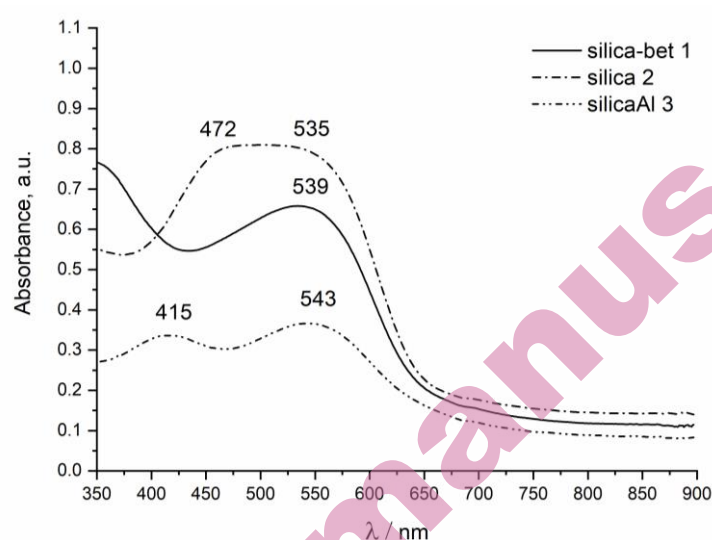


Fig. 4. UV-Vis spectra of the beetroot dye formulations based on silica and aluminosilicate

Effect of  $\text{NH}_3$  vapors on dye-carrier formulations color change  
Mean  $L^*$   $a^*$   $b^*$  values for the dye loaded powders before and after ammonium exposure are presented in table II.

Table II. Color parameters for beet juice in different matrices before and after exposure to base atmosphere

Sample	Color parameters before exposure			Color parameters in $\text{NH}_3$ atmosphere			$\Delta E$
	$L^*$	$a^*$	$b^*$	$L^*$	$a^*$	$b^*$	
Silica 2	$84.78 \pm 0.43$	$4.49 \pm 0.17$	$-1.16 \pm 0.03$	$83.13 \pm 0.29$	$3.60 \pm 0.14$	$0.70 \pm 0.08$	1.87
SilicaAl 3	$86.21 \pm 0.35$	$3.69 \pm 0.38$	$-1.78 \pm 0.01$	$86.34 \pm 0.11$	$1.99 \pm 0.05$	$0.25 \pm 0.08$	2.65
Silica-bet1	$80.02 \pm 0.21$	$7.68 \pm 0.12$	$-0.24 \pm 0.01$	$85.12 \pm 0.47$	$2.80 \pm 0.20$	$1.72 \pm 0.27$	7.32

\*Data are presented as mean  $\pm$  standard deviation of triplicate analyses

The other parameter in Table II,  $\Delta E$ , is the color difference between before ( $L_0$ ,  $a_0$ ,  $b_0$ ) and after exposure to  $\text{NH}_3$  ( $L$ ,  $a$ ,  $B$ ) and was determined using the following equation.<sup>25</sup>

$$\Delta E = [(L_0 - L)^2 + (a_0 - a)^2 + (b_0 - b)^2]^{1/2}$$

The values of the color parameters presented above indicate that the as prepared matrices containing beet juice are different, silica-bet 1 and silica 2 are redder while silicaAl 3 is lighter and yellower. Values  $\Delta E$  between 1.5 -3 (silica 2 and silicaAl 3 sample) indicate distinct and over 6 (silica-bet 1 sample) great differences between the initially prepared samples and the ones exposed to ammonia.<sup>26</sup>

#### CONCLUSION

Betalains pigments were included in silica and respectively aluminosilicate carriers to stabilize and improve their properties for practical applications. The direct encapsulation approach enabled the incorporation of other natural occurring compounds besides the dye, such as the complex forming  $\beta$ -CD and ascorbic acid, upgrading thus the prepared formulation regarding the color properties and the color variation with pH change. Structure directing agents generated mesoporous silica and zeolite Y-type supports with a complex, regular pore layout for the colorant adsorption. Betalains color properties depend on the variation in the physico-chemical characteristics of the micro/mesoporous supports.

ИЗВОД  
ИМОБИЛИЗАЦИЈА ПРИРОДНИХ БЕТАЛАИНСКИХ ПИГМЕНАТА У НЕОРГАНСКИМ  
МАТЕРИЈАЛИМА

LIGIA TODAN<sup>1</sup>, DANIELA C CULITA<sup>1</sup>, MIRABELA E. SOARE<sup>1</sup>, RODICA M. ION<sup>2</sup>, RADU C. FIERASCU<sup>2</sup> И MARIA MAGANU<sup>3</sup>

<sup>1</sup>Ilie Murgulescu Institute of Physical Chemistry, Romanian Academy, 202 Splaiul Independentei, 060021 Bucharest, Romania, <sup>2</sup>National Institute for Research & Development in Chemistry and Petrochemistry-ICECHIM, 202 Splaiul Independentei, 060021 Bucharest, Romania, и <sup>3</sup>„Costin D. Nenitescu” Institute of Organic and Supramolecular Chemistry, Romanian Academy, 202 B Splaiul Independentei, 060023 Bucharest, Romania

У циљу испитивању нових рН осетљивих формулација хране, екстракт црвене цвекле богат бетацијанином, ради побољшања стабилности његове боје, је наношен на различите неорганске подлоге које садрже силицијум-диоксид и алуминосиликате. Директном методом инкапсулације пигмента на неорганску подлогу која садржи силицијум-диоксид и алуминосиликат додат је стабилизатор који представља инклузиони комплекс  $\beta$ -циклодекстрина и аскорбинске киселине. Систем накнадног пуњења укључује синтезу порозног силицијум-диоксид и алуминосиликатног праха и адсорпцију екстракта репе на овим подлогама. Пре наношења екстракта извршена је структурна карактеризација неорганске подлоге (дифракција рендгенских зрака, FTIR и N<sub>2</sub>-физиорпција). Присуство бетанина (одобрен као црвена боја за храну) у испитиваним узорцима је одређено применом UV-Vis спектроскопије. Испитиване су промене боје, као и рН генерисане промене боје прахова изложених дејству амонијака при врху капсулираних посуда. Добијени резултати могу допринети већој примени екстракта репе, док предложене еколошке формулације могу бити од значаја код паковања хране.

(Примљено 28. октобра 2022; ревидирано 21. јануара 2023; прихваћено 1. марта 2023.)

REFERENCES

1. S. Chethana, C. A. Nayak, K. S. M. S. Raghavarao, *J. Food Eng.* **81** (2007) 679 (<https://doi.org/10.1016/j.jfoodeng.2006.12.021>)
2. S. Akan, Ö. Horzum, H. C. Akal, *LWT-Food Sci. Technol.* **155** (2022) 112877 (<https://doi.org/10.1016/j.lwt.2021.112877>)
3. P. S. Grewal, C. Modavi, Z. N. Russ, N. C. Harris, J. E. Dueber, *Metab. Eng.* **45** (2018) 180 (<https://doi.org/10.1016/j.ymben.2017.12.008>)
4. O. L. Torres Vargas, Y. V. Galeano Loaiza, M. L. González, *J. Mater. Res. Technol.* **13** (2021) 2239 (<https://doi.org/10.1016/j.jmrt.2021.05.091>)
5. M. I. Khan, *Food Chem.* **197** (2016) 1280 (<https://doi.org/10.1016/j.foodchem.2015.11.043>)
6. S. J. Calva-Estrada, M. Jiménez-Fernández, E. Lugo-Cervantes, *Food Chemistry: Molecular Sciences* **4** (2022) 100089 (<https://doi.org/10.1016/j.fochms.2022.100089>)

7. S. Li, B. Mu, X. Wang, A. Wang, *Dyes Pigments* **190** (2021) 109322 (<https://doi.org/10.1016/j.dyepig.2021.109322>)
8. E. Pérez-Ramírez, E. Lima, A. Guzmán, *Dyes Pigments* **120** (2015) 161 (<https://doi.org/10.1016/j.dyepig.2015.03.040>)
9. E. S. Dolinina, E. Yu. Akimsheva, E. V. Parfenyuk, *J. Mol. Liq.* **287** (2019) 110938 (<https://doi.org/10.1016/j.molliq.2019.110938>)
10. E. Akbar Hussain, Z. Sadiq, M. Zia-Ul-Haq, *Betalains: Biomolecular Aspects*, Springer International Publishing, Cham, 2018, p. 125 (<https://doi.org/10.1007/978-3-319-95624-4>)
11. F. Billmeyer, M. Saltzman, *Principles of color technology*, John Wiley & Sons, New York, 2000, p. 1
12. W. Simanjuntak, S. Sembiring, P. Manurung, R. Situmeang, I. M. Low, *Ceram. Int.* **39** (2013) 9369 (<https://doi.org/10.1016/j.ceramint.2013.04.112>)
13. D. Paudel, R. Atta-Fynn, D. A. Drabold, S. R. Elliott, P. Biswas, *Phys. Rev. B* **97** (2018) 184202. (<https://doi.org/10.1103/physrevb.97.184202>)
14. D. Orthaber, A. Bergmann, O. Glatter, *J. Appl. Crystallogr.* **33** (2000) 218 (<https://doi.org/10.1107/S0021889899015216>)
15. C. Boissière, L. Nicole, C. Gervais, F. Babonneau, M. Antonietti, H. Amenitsch, C. Sanchez, D. Grosso, *Chem. Mater.* **18** (2006) 5238 (<https://doi.org/10.1021/cm061489j>)
16. M. Król, A. Koleżyński, W. Mozgawa, *Molecules* **26** (2021) 342 (<https://doi.org/10.3390/molecules26020342>)
17. E. M. Flanigen, L. B. Sand, eds., *Molecular Sieve Zeolites-I*, American Chemical Society, WASHINGTON, D. C., 1974, p. 201 (<https://doi.org/10.1021/ba-1971-0101.ch016>)
18. J. Yang, Y.-X. Huang, Y. Pan, J.-X. Mi, *Micropor. Mesopor. Mater.* **303** (2020) 110247 (<https://doi.org/10.1016/j.micromeso.2020.110247>)
19. F. Gandía-Herrero, J. Escribano, F. García-Carmona, *Planta* **232** (2010) 449 (<https://doi.org/10.1007/s00425-010-1191-0>)
20. F. C. Stintzing, R. Carle, *Trends Food Sci. Technol.* **15** (2004) 19 (<https://doi.org/10.1016/j.tifs.2003.07.004>)
21. I. Belhadj Slimen, T. Najar, M. Abderrabba, *J. Agric. Food Chem.* **65** (2017) 675 (<https://doi.org/10.1021/acs.jafc.6b04208>)
22. I. Sadowska-Bartosz, G. Bartosz, *Molecules* **26** (2021) 2520 (<https://doi.org/10.3390/molecules26092520>)
23. C. Karavasili, E. Kontogiannidou, A.-T. Chatzitaki, P. Bampalexis, D. G. Fatouros, *Micropor. Mesopor. Mater.* **305** (2020) 110343 (<https://doi.org/10.1016/j.micromeso.2020.110343>)
24. S. Nastase, L. Bajenaru, C. Matei, R. A. Mitran, D. Berger, *Micropor. Mesopor. Mater.* **182** (2013) 32 (<https://doi.org/10.1016/j.micromeso.2013.08.018>)
25. N. K. Kortei, G.T. Odamten, M. Obodai, V. Appiah, P.T. Akonor, *Croatian journal of food technology, biotechnology and nutrition* **10** (1-2) (2015) 66.
26. M. Cruz-Romero, A. L. Kelly, J. P. Kerry, *Innov. Food Sci. Emerg. Technol.* **8** (2007) 30 (<https://doi.org/10.1016/j.ifset.2006.05.002>)



*J. Serb. Chem. Soc.* **00(0)**S1-S3 (2022)

Journal of  
the Serbian *el* version  
Chemical Society *ectronic*

JSCS-info@shd.org.rs • www.shd.org.rs/JSCS

*Supplementary material*

SUPPLEMENTARY MATERIAL TO

Accepted manuscript